

Chapter 2

Green synthesis of gold nanoparticles using *Wendlandia wallichii*, a potent wild edible plant consumed by the tribal of North-Eastern region in India

2.1. Introduction:

In the last decade, nanoscience and nanotechnology appear to be one of the most busy areas of research and development around the globe. In fact, nanoscience holds key to plethora of technological and environmental problems like solar energy conversion, catalysis, biomedical science, opto-electronics and water treatment^{1,2}. The noble metal nanoparticles especially of silver and gold have been exploited for their versatile applications in various fields such as catalysis, optics, sensing, imaging, and biomedical science³. The ordinary materials, when reduced to the nanoscale, often exhibit novel and unpredictable characteristics such as extraordinary strength, chemical reactivity, electrical conductivity, super-paramagnetic behavior and other characteristics that the same material does not possess at the micro- or macroscale⁴. It is known that the size, morphology, stability and properties of the MNPs are strongly influenced by the experimental conditions, the kinetics of interactions of metal ions with the reducing agents and adsorption processes of stabilizing agents with MNPs.

There are different methods for the synthesis of MNPs, such as, chemical⁵, photochemical⁶, sonochemical⁷, radiochemical⁸, electrochemical⁹ and biological methods¹⁰. But the chemical method is the most commonly used ones to get nanoparticles as stable dispersions in water or organic solvents¹¹. However, the method suffers from the drawback that the chemical reductant and stabilizer cause environmental toxicity thereby limiting its use in biomedical science¹². In recent years, plant-mediated biological synthesis of nanoparticles is gaining importance due to its simplicity and eco-friendliness. Such bio-synthesis provides improvement over other methods as it is simple, one step, cost-effective, environment friendly and easily reproducible.^{13,14} The diversity of plant extracts and types

Chapter 2: Green synthesis of gold nanoparticles using *Wendlandia wallichii*

of metal salts, the ability to alter the composition of a reaction mixture and reaction conditions through changes in the temperature, pH, and inclusion of additives of biological origin (bio-matrices), allow us to produce nanoparticles of various metals with a defined size and shape.

The metallic nanoparticles exhibit various size and shape-dependent optical properties, which are useful in various biomedical applications like the imaging of specific target cells and tissues, drug delivery, bio-sensing and catalysts to optics.^{15,16} The nanoparticles are of immense interest due to their extremely miniscule size and high surface area to volume ratio, which lead to both chemical and physical differences in their properties compared to the bulk having the same composition.^{17,18}

The Gold nanoparticles (AuNPs) are of special interest mainly due to the relative ease of their synthesis, with good control of their sizes and shapes, their optical characteristics and their good bio-compatibility. Plant-based synthesis of AuNPs, via the reduction of Au (III), is relatively faster, and safer and does not require any additional stabilizer. Moreover, the synthesis can be carried out at room temperature without the aid of high physical and instrumental requirements under easy to handle and easy to scale-up and reaction procedures. The Gold nanoparticles have been widely investigated because of their uniqueness especially in bio-medication and in bio-imaging. These biologically synthesized nanoparticles have wide applications in different areas, such as treatment, diagnosis, development of surgical nanodevices¹⁹. Nano-medicine makes a revolutionary impact in healthcare sector in treating different chronic diseases. Thus eco-friendly synthesis of nanoparticles is regarded as building blocks of the forthcoming generations to control different diseases²⁰. However, the mixture of AuNPs and green reductants may

possibly result in synergistic biological activities. Different plant parts such as , roots, stems, bark, leaves and petals can be exploited as reducing as well as stabilizing agents in the green synthesis of AuNPs^{21,22}.

2.2. Materials and Methods:

2.2.1 Plant materials

The leaves of *W. wallichii* were collected from Meghalaya state, India in December, 2015 and identification was authenticated in our office of Shibpur Botanical garden, Shibpur, India. The voucher specimens were preserved in the Plant Chemistry department of our office under registry no BSITS 104. The plant parts were shed-dried, pulverized and stored in an airtight container for further extraction.

2.2.2 Chemicals

The standard phenolic acids (gallic acid, protocatechuic acid, gentisic acid, chlorogenic acid, *p*-hydroxy benzoic acid, vanillic acid, caffeic acid, syringic acid, *p*-coumaric acid, ferulic acid, sinapic acid, salicylic acid and ellagic acid), flavonoids (catechin, rutin, myricetin, quercetin, naringin, apigenin and kaempferol), 1,1-Diphenyl-2-picrylhydrazyl (DPPH), 2,2'-azino-bis(3-ethylbenzothiazoline-6-sulfonic acid) (ABTS), butylated hydroxytoluene (BHT) were procured from Sigma Chemical Co. (St. Louis , MO , USA). Folin-Ciocalteus's phenol reagent, potassium ferricyanide, potassium per sulphate, aluminium chloride, ferric chloride , anthrone, sodium carbonate, HPLC-grade solvents (acetonitrile, methanol, water and trifluoroacetic acid), sodium dihydrogen phosphate were purchased from Merck (Germany).Tetrachloroauric acid (HAuCl₄) was purchased from SRL. All the chemicals and solvents used were of analytical grade.

2.2.3 HPLC equipment

Dionex Ultimate 3000 liquid chromatograph attached with a diode array detector (DAD) was taken for HPLC analysis. The separation of components was achieved by a reversed-phase Acclaim C18 column (5 micron particle size, 250 x 4.6 mm). 20 μ L of sample was injected into the HPLC column. The Chromeleon system manager was used for analyzing the data.

2.2.4 Proximate composition and minerals content in *W. wallichii*

2.2.4.1 Estimation of ash content

Five gm of powdered leaves of the plant were taken in a silica crucible and heated for about 5-6h in a muffle furnace controlled at 500°C. The crucible was cooled, weighed and heated again in the furnace for half an hour. This process was repeated consecutively until the weight of the crucible along with the sample became constant (ash became white or greyish white). Weight of ash gave the ash content²³. The ash obtained was preserved for mineral analysis.

$$\text{Ash content (\%)} = \text{Weight of ash} \times 100 / \text{Weight of sample}$$

2. 2.4.2 Estimation of moisture content

The moisture content of the plant sample was carried out by heating a known amount of fresh leaves in an air oven at 100-110°C and weighed. The loss in weight was considered as a measure of moisture content in the sample²³.

$$\text{Moisture (\%)} = [(\text{Weight of original sample} - \text{Weight of dried sample})] \times 100 / \text{Weight of original sample}$$

2.2.4.3 Estimation of crude fat content

Two gm of moisture free leaves were soxhleted with petroleum ether (40-60°C) for about 6-8h. The petroleum ether extract was filtered and evaporated in a pre-weighed beaker. Increase in weight of the beaker determines the crude fat content. Percentage of the fat content was calculated using the following formula ²³.

$$\text{Crude fat (\%)} = \text{Weight of fat in sample} \times 100 / \text{Weight of dry sample}$$

2.2.4.4 Estimation of crude fibre content

The crude fibre content in the plant sample was carried out by warming two gm of moisture and fat-free leaves with 200ml of 1.25% sulphuric acid followed by 1.25% sodium hydroxide solution and with 1% nitric acid. The solution was filtered and the residue was washed with boiling water and then the residue was dried in an oven at 130°C to constant weight. The residue was heated in a muffle furnace at 550°C for two hours, cooled in a desiccators and weighed. The crude fibre content was expressed as percentage loss in weight on ignition ²³.

$$\text{Crude fibre (\%)} = (\text{Weight of residue} - \text{Weight of ash}) \times 100 / \text{Weight of the sample}$$

2.2.4.5 Estimation of crude protein content

The micro Kjeldahl method was adopted for the estimation of crude protein content in the plant where two gm of samples were digested with concentrated sulphuric acid in a Kjeldahl flask in the presence of 0.5 gm CuSO₄ and 5 gm K₂SO₄, until a clear solution was obtained. The digested solution was cooled and diluted with distilled water and an excess of sodium hydroxide solution (40%) was added to the diluted reaction mixture, the

liberated ammonia was distilled in steam and absorbed in 25 ml (N/20) sulphuric acid. The excess mineral acid was titrated with known strength of sodium hydroxide and from this, the percentage of nitrogen in the sample was calculated. The amount of protein content was determined by multiplying the amount of nitrogen with 6.25²³.

2.2.4.6 Estimation of carbohydrate content

100 mg of leaves were hydrolyzed with 5 ml of hydrochloric acid (2.5 N), cooled to room temperature and neutralized with solid sodium carbonate until the effervescence ceases. The solution was filtered in a 100 ml volumetric flask and the volume was made up with distilled water. To 1 ml of this solution, 4 ml freshly prepared anthrone reagent (200 mg anthrone dissolved in 100 ml of ice-cold 95% sulphuric acid) were added and heated in a water bath for eight minutes. The mixture was cooled rapidly, a dark green colour appeared and the absorption at 630 nm was measured (UV-visible spectrophotometer Shimadzu UV 1800). The total carbohydrate content was expressed as glucose equivalents using the following equation based on the calibration curve $y = 0.0081x + 0.2475$, $R^2 = 0.9993$ where y was the absorbance and x concentration of glucose in mg/ml²⁴.

2.2.4.7 Estimation of energy content

The energy (kcal/100gm) content of the plant sample was determined by multiplying the values obtained for protein, fat and available carbohydrate by 4.00, 9.00 and 4.00, respectively and adding up the values²⁵.

2.2.4.8 Estimation of minerals

One gram of ash of the plant obtained above was dissolved in 30 ml of hydrochloric acid (5 %) solution, filtered and volume made up to 50 ml with double distilled water and minerals were estimated in atomic absorption spectrophotometer (AAS) (AA 800, Perkin-Elmer, Germany). The standard solution of each element was prepared and calibration curves were drawn for each element using AAS²⁶. All assays were carried out in triplicate and values were obtained by calculating the average of three experiments and data are presented as Mean \pm SEM.

2.2.4.9 Antioxidant activities of *W. wallichii*

2.2.4.9.1. Extraction of plant material (Benzene, chloroform, acetone and methanol)

One gram of each plant materials were extracted with 20 ml each of benzene, chloroform, acetone and methanol with agitation for 18-24 h at ambient temperature. The extracts were filtered and diluted to 50 ml and aliquot were analyzed for their total phenolic, flavonoid and flavonol content, reducing power and their free radical scavenging capacity.

2.2.4.9.2 Estimation of total phenolic content

The amount of total phenolic content of the crude extracts was determined according to Folin-Ciocalteu procedure²⁷. The tested samples (20 - 100 μ l) were taken into test tubes. 1 ml of Folin-Ciocalteu reagent and 0.8 ml of sodium carbonate (7.5%) were added. The tubes were mixed and allowed to stand for 30 min. Absorption at 765 nm was measured (UV-visible spectrophotometer Shimadzu UV 1800). The total phenolic content was expressed as gallic acid equivalents (GAE) in milligram per gram (mg/g) of extract using

the following equation based on the calibration curve $y = 0.0013x + 0.0498$, $R^2 = 0.999$ where y was the absorbance and x was the Gallic acid equivalent (mg/g).

2.2.4.9.3 Estimation of total flavonoids

Total flavonoids were estimated using the method mentioned at Seal *et al.*, 2015²⁷. To 0.5 ml of sample, 0.5 ml of 2% AlCl₃ in ethanol was added. After one hour, at room temperature, the absorbance was measured at 420 nm (UV-visible spectrophotometer Shimadzu UV 1800). A yellow colour indicated the presence of flavonoids. Total flavonoid contents were calculated as rutin equivalent (mg/g) using the following equation based on the calibration curve: $y = 0.0182x - 0.0222$, $R^2 = 0.9962$, where y was the absorbance and x was the Rutin equivalent (mg/g).

2.2.4.9.4 Estimation of total flavonols

Total flavonols in the plant extracts were estimated using the method stated at Seal *et al* 2017²⁸. To 2.0 ml of sample (standard), 2.0 ml of 2% AlCl₃ ethanol and 3.0 ml (50 g/L) sodium acetate solutions were added. The absorption at 440 nm (UV-visible spectrophotometer Shimadzu UV 1800) was read after 2.5 h at 20°C. Total flavonol content was calculated as quercetin equivalent (mg/g) using the following equation based on the calibration curve: $y = 0.0049x + 0.0047$, $R^2 = 0.9935$, where y was the absorbance and x was the quercetin equivalent (mg/g).

2.2.4.9.5 Measurement of reducing power

The reducing power of the extracts was determined according to the method described by Seal *et al*, 2017²⁸. Extracts (100 µl) of plant extracts were mixed with phosphate buffer

(2.5 ml, 0.2 M, pH 6.6) and 1% potassium ferricyanide (2.5 ml). The mixture was incubated at 50°C for 20 min. Aliquots of 10% trichloroacetic acid (2.5 ml) were added to the mixture, which was then centrifuged at 3000 rpm for 10 min. The upper layer of the solution (2.5 ml) was mixed with distilled water (2.5 ml) and a freshly prepared ferric chloride solution (0.5 ml, 0.1%). The absorbance was measured at 700 nm. Reducing power is given in ascorbic acid equivalent (AAE) in milligram per gram (mg/g) of dry material using the following equation based on the calibration curve: $y = 0.0023x - 0.0063$, $R^2 = 0.9955$ where y was the absorbance and x was the ascorbic acid equivalent (mg/g).

2.2.4.9.6 Determination of DPPH free radical scavenging activity

The free radical scavenging activity of the plant samples and butylated hydroxyl toluene (BHT) as positive control was determined using the stable radical DPPH (1,1-diphenyl-2-picrylhydrazyl)²⁸. Aliquots (20 -100 μ l) of the tested sample were placed in test tubes and 3.9 ml of freshly prepared DPPH solution (25 mg L⁻¹) in methanol was added in each test tube and mixed. The absorbance was measured at 517 nm (UV-visible spectrophotometer Shimadzu UV 1800) after 30 min. The capability to scavenge the DPPH radical was calculated, using the following equation:

$$\text{DPPH scavenged (\%)} = \{(A_c - A_t)/A_c\} \times 100$$

Where A_c is the absorbance of the control reaction and A_t is the absorbance in presence of the sample of the extracts. The antioxidant activity of the extract was expressed as IC_{50} . The IC_{50} value was defined as the concentration in mg of dry material per ml (mg / ml) that inhibits the formation of DPPH radicals by 50%. Each value was determined from regression equation.

2.2.4.9.7 Scavenging activity of ABTS radical cation

The 2,2'-azino-bis(3-ethylbenzothiazoline-6-sulfonic acid) (ABTS) radical cation (ABTS^{•+})-scavenging activity was measured according to the method described by Seal *et al*²⁸. ABTS was dissolved in water to a 7 mM concentration. The ABTS radicals were produced by adding 2.45 mM potassium persulphate (final concentration). The completion of radical generation was obtained in the dark at room temperature for 12–16 h. This solution was then diluted with ethanol to adjust its absorbance at 734 nm to 0.70 ± 0.02. To determine the scavenging activity, 1 ml of diluted ABTS^{•+} solution was added to 10 µl of plant extract (or water for the control), and the absorbance at 734 nm was measured 6 min after the initial mixing, using ethanol as the blank. The percentage of inhibition was calculated by the equation:

$$\text{ABTS scavenged(\%)} = (A_{\text{cont}} - A_{\text{test}}) / A_{\text{cont}} \times 100$$

Where, A_c and A_t are the absorbencies of the control and of the test sample, respectively.

From a plot of concentration against % inhibition, a linear regression analysis was performed to determine the IC₅₀ value of the sample.

2.2.4.10 Quantification of phenolic acids and flavonoids in the methanol extract of *W. wallichii* by HPLC

2.2.4.10.1 Preparation of standard solutions

The stock solution of gallic acid of concentration 1mg / ml was prepared by dissolving 10 mg gallic acid in 1 ml HPLC-grade methanol followed by sonication for 10 min and the resulting volume was made up to 10 ml with the solvent for the Mobile phase (methanol

and 0.5% aq. acetic acid 1:9). The same method was followed to prepare the standard stock solutions of the phenolic acids and the flavonoids *viz.* protocatechuic acid, gentisic acid, chlorogenic acid, *p*-hydroxy benzoic acid, vanillic acid, caffeic acid, syringic acid, *p*-coumaric acid, ferulic acid, sinapic acid, salicylic acid and ellagic acid, catechin, rutin, myricetin, quercetin, naringin, apigenin and kaempferol. The working standard solutions of concentrations 20, 40, 60, 80 and 100µg/ml were prepared by further dilution of the standard solution with the mobile phase solvent system. The standard and working solutions were filtered through 0.45 µm PVDF-syringe filter and the mobile phase was degassed before the injection of the solutions.

2.2.4.10.2 Chromatographic analysis for the quantification of phenolic acids and flavonoids

The HPLC analyses for the quantification of phenolic acids and flavonoids in the plant extract were performed following the method described by Seal 2016 with minor modification²⁸. The analyses were carried out using Dionex Ultimate 3000 liquid chromatograph including a diode array detector (DAD) with 5 cm flow cell and with Chromeleon system manager as data processor. The separation was achieved by a reversed phase Acclaim C18 column (5 micron particle size, 250 x 4.6 mm). 20 µL of sample was introduced into the HPLC column. The method was validated according to the USP and ICH guidelines^{29,30}. The mobile phase contains methanol (Solvent A) and 0.5% aq. acetic acid solution (Solvent B) and the column was thermostatically controlled at 25 °C and the injection volume was kept at 20 µL. A gradient elution was performed by varying the proportion of solvent A to solvent B. The gradient elution was 10 % A and 90% B with

Chapter 2: Green synthesis of gold nanoparticles using *Wendlandia wallichii*

flow rate 1 ml/min to 0.7 ml/min in 27 min, from 10 to 40 % A with flow rate 0.7 ml/min for 23 min, 40% A and 60% B with flow rate 0.7 ml/min initially for 2 min and then flow rate changed from 0.7 to 0.3 ml/min in 65min, from 40 to 44% A with flow rate 0.3 to 0.7ml/min in 70 min, 44% A with flow rate 0.7 to 1ml/min for 10 min duration, solvent A changed from 44% to 58 % with flow rate 1ml/min for 5 min, 58 to 70% A in 98 min at constant flow rate 1 ml/min. The mobile phase composition back to initial condition (solvent A: solvent B: 10: 90) in 101 min and allowed to run for another 4 min, before the injection of another sample. Total analysis time per sample was 105 min.

HPLC chromatograms were detected using a photo diode array UV detector at three different wavelengths (272, 280 and 310 nm) according to absorption maxima of analysed compounds. Each compound was identified by its retention time and by spiking with standards under the same conditions. The quantification of phenolic acids and flavonoids in the leaves of the plant were carried out by the measurement of the integrated peak area and the contents were calculated using the calibration curve by plotting peak area against concentration of the respective standard sample.

2.2.4.11 Biosynthesis of gold nanoparticles using methanol extract of *W. wallichii*

2.2.4.11.1 Preparation of Au (III) solution

HAuCl₄ was purchased from SRL (Sisco Research Laboratory) and used without further purification. HAuCl₄ (52.8 mg) was dissolved in de-ionized water (10 ml) to obtain a 13.4 mM Au(III) stock solution.

2.2.4.11.2 Preparation of the leaf extract of *W. wallichii*

Finely powdered leaves of *W. wallichii* (3 gm) was suspended in methanol (10 ml) in a test tube, sonicated in an ultrasonicator bath for 45 min and then centrifuged for 10 minutes to obtain a clear supernatant. To know the concentration of the leaf extract, an aliquot of the clear supernatant (2 ml) was taken in a round bottom flask and the volatiles were removed under reduced pressure to afford a sticky solid (16.8 mg). Thus the concentration of the leaf extract was 8400 mg L⁻¹³¹.

2.2.4.11.3 Synthesis of Gold Nanoparticles of the leaf extract of *W. wallichii*

Aliquots of Au (III) solution (0.2 ml, 13.4 mM each) were added drop-wise to the solution of leaf extract of *W. wallichii* to prepare a series of stabilized AuNPs where concentration of the extract were 100, 200, 300 and 400 mgL⁻¹ and the concentration of Au (III) was fixed at 0.67 mM. UV-visible spectroscopy of the solutions was carried out after 24 h of HAuCl₄ and the leaf extract of the plant had been mixed³¹.

2.2.4.11.4 Characterization

TEM images, SAED and EDX of AuNPs were taken from Technal G 2 instrument. UV-visible spectra were recorded in Shimadzu 1601 spectrophotometer.

2.3. Results and Discussion

2.3.1 Proximate composition and minerals content in *W. wallichii* :

The leaves of *W. wallichii* were taken for the analysis of proximate composition. The proximate composition of these plants is appended in Table 1.

The proximate analysis of the plant showed that 100gm of dry plant contain 7.19±0.15 gm ash and 83.53±0.19 gm moisture. The high amount of ash content indicating that this plant

was rich in minerals and could provide a substantial amount of mineral elements to our diet³².

Table 1. Proximate composition and minerals content in *W. Wallichii*

Proximate composition	Amount	Minerals	Amount (mg/g)
Ash (%)	7.19±0.15	Sodium (Na)	0.98±0.09
Moisture (%)	83.53± 0.19	Potassium (K)	13.61±0.25
Protein (%)	6.48±0.04	Calcium (Ca)	18.38±0.34
Fat (%)	2±0.06	Copper (Cu)	BDL
Carbohydrate (%)	24.09±0.14	Zinc (Zn)	0.044±0.00015
Crude fibre (%)	11.66±0.24	Magnesium (Mg)	0.56±0.003
Energy (kcal/100gm)	76.02±0.70	Iron (Fe)	0.018±0.001
		Manganese (Mn)	0.0128±0.0005

Each value in the table was obtained by calculating the average of three experiments and data are presented as Mean ± SEM

The plant was found to contain protein, fat, fibre and carbohydrate 6.48±0.04%, 2 ± 0.06%, 11.66 ± 0.24% and 24.09 ± 0.14 % respectively. The energy content of the plant was calculated at 76.02 ± 0.7 kcal/100gm. The fat and fibre content in the plant was particularly high and well compared to that reported for some common vegetables which indicates that the consumption of the plant would be helpful for the absorption of fat soluble vitamins like vitamin A and carotene in the body and might play an important role in decreasing the risks of many disorders such as constipation, diabetes, serum cholesterol, heart diseases,

breast and colon cancer, hypertension, etc. ^{33,34}. The plant is a rich source of protein which can encourage their use in human diets and would be helpful for the proper functioning of antibodies resisting infection³³.

Fruits, and vegetables, are important sources of macro-minerals (Na, K, Ca Mg) and micro-minerals (Fe, Zn, Cu, Mn, Zn, Pb, Cr) which are responsible in maintaining physiological and biological functions of the human body. The leaves of the plant contain a very good amount of sodium (0.98 ± 0.09 mg/gm) and potassium (13.61 ± 0.25 mg/gm). The ratio of K/Na was significant in this plant (13.89) which is very much responsible to control the high blood pressure of our body³⁵. The leaves of the plant was found to contain 18.38 ± 0.34 mg/g calcium which might be beneficial to build strong and healthy bones and also required for the normal functioning of the cardiac muscles ²⁷. A sufficient amount of Cu, Zn, Mg, Fe and Zn were present in the plant indicating that the consumption of this vegetable might be helpful for preventing iron- deficiency anaemia, nucleic acid metabolism, control the blood- glucose levels and support a healthy immune system^{36,37}.

2.3.2 Antioxidant activities of the different solvent extracts of *W. wallichii* :

2. 3.2.1 Extractive value

The extractive values of the plant under investigation with four different solvents are shown in table 2. The result indicates that, methanol is the most suitable solvent to obtain the maximum extract from the plant under investigation in comparison to other solvents like benzene, chloroform and acetone used for extraction. The leaves of *W. wallichii* give maximum yield (12.85 ± 0.08 g/100g) when it is extracted with methanol and the least amount is observed with benzene. The differences in the extractive value of the plant

materials may be due to the varying nature of the chemical components present and the polarities of the solvent used for extraction.

Table 2.Antioxidant activities of *W. wallichii* using different solvents

	Benzene	Chloroform	Acetone	Methanol
Extractive value (%)	0.6±0.005	1.025±0.06	2.4±0.03	12.85±0.08
Total phenolic content (Gallic acid equivalent, mg/100gm Plant material)	27.30±3.7	54.23±5.41	801.66±2.28	5050±1.14
Total Flavonoid content (Rutin equivalent mg/100gm Plant material)	24.38±0.55	49.61±1.2	98.15±0.08	454.34±0.51
Total flavonol content (Quercetin equivalent mg/100gm Plant material)	21.07±0.85	36.37±0.57	55.08±0.49	373.21±0.57
Reducing power (Ascorbic acid equivalent mg/100gm Plant material)	26.05±6.8	20.25±3.08	101.41±1.88	628.44±3.49
DPPH radical scavenging activity (IC50 mg dry extract)	2.96±0.26	1.18±0.04	0.05±0.0002	0.012±0.0001
ABTS radical scavenging activity (IC50 mg dry extract)	0.27±0.004	0.22±0.015	0.05±0.0001	0.011±0.0001

Each value in the table was obtained by calculating the average of three experiments and data are presented as Mean ± SEM

2.3.2.2 Total phenol, flavonoid and flavonol content in the extract

The screening of the benzene, chloroform, acetone and methanol extracts of the plants revealed that highest amount of phenolic compounds, flavonoid and flavonol were detected in the methanol extract of the plant. The results strongly suggest that phenolics are important components of these plants. The other phenolic compounds such as flavonoids, flavonols, which contain hydroxyls are responsible for the radical scavenging effect in the plants. According to our study, methanol was the most suitable solvent to isolate the phenolic compounds and benzene, chloroform and acetone are the best solvent to isolate

the flavonoids and flavonols from the plant materials. The total phenolic component exhibited antioxidant activity through adsorption and neutralization of the free radicals, whereas, flavonoid and flavonol showed antioxidant activity through scavenging or chelating process^{38,39}. The high content of the phenolic compounds in *W. wallichii*, can explain their high radical scavenging activity. In this study the methanol extract of *W. wallichii* showed potent antioxidant activities using DPPH and ABTS assay. The IC₅₀ value of DPPH assay of *W. wallichii* was found to be higher than that of ABTS assay which showed more antioxidant activities. The high radical scavenging property of this plant may be due to the presence of hydroxyl groups that can provide the necessary component as a radical scavenger.

The antioxidant activities of the extractive solution represent an important parameter to evaluate the biological property of the plant. Therefore, it is necessary to characterize and quantify the important compounds like phenolic acids and flavonoids present in the plant and also to validate the method of separation and identification of active constituents.

The HPLC analysis showed (Fig.1, Table 3) the presence of remarkable amount of catechin (2.52 ± 0.08 mg/gm plant material) in the methanol extract of *W. wallichii*. Due to the presence of *p*-coumaric acid (0.043 ± 0.002 mg/gm), the plant is believed to have antioxidant behavior thereby reducing the formation of carcinogenic nitrosamines in the stomach⁴⁰.

The plant was found to contain a very good amount of chlorogenic acid (0.005 ± 0.0001 mg/gm) which is responsible for reducing hepatic triglycerides levels, thus resulting in weight loss. It also decreases proliferation of new fat cells through its antioxidant effects⁴¹.

Chapter 2: Green synthesis of gold nanoparticles using *Wendlandia wallichii*

Syringic acid with hydroxy benzoic acid skeleton was found in the plant under investigation (0.088 ± 0.009 mg/gm) was higher than that reported for common leafy vegetables, such as, cauliflower (0.0113 mg/gm) *Salvia officinalis* (0.0335 mg/gm), *Origanum vulgare* (0.0375 mg/gm) and this phenolic acid is well known for its anti-cancer, anti-proliferative, sedative, decongestant and hepato-protective actions⁴².

An appreciable amount of quercetin (0.024 ± 0.001 mg/gm), detected in *W. wallichii* were comparable to the same in apple (0.021 mg/gm), lettuce (0.011 mg/gm) and tomato (0.055 mg/gm) and this is reported to display anti-histamine, anticancer as also anti-inflammatory activities^{43,44}.

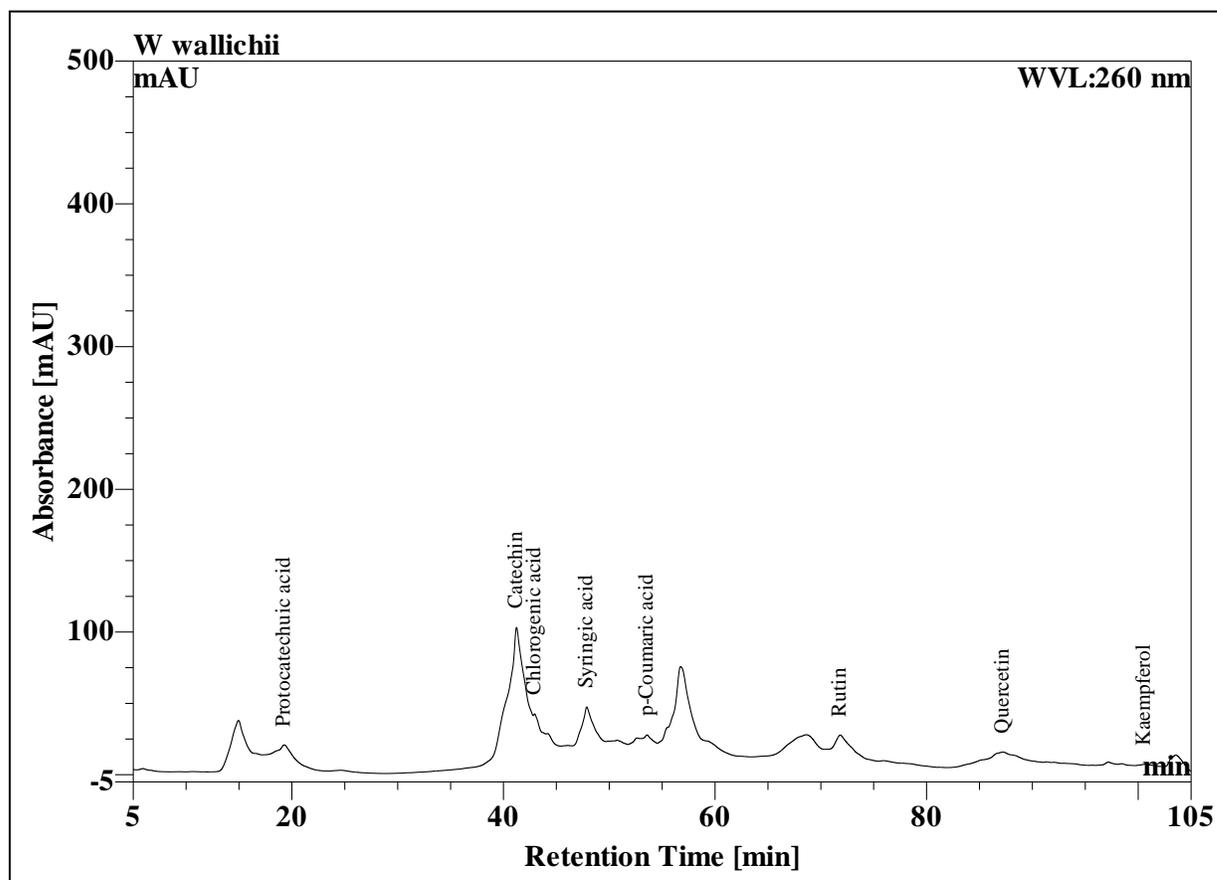


Fig.1. HPLC chromatogram for the quantification of phenolic acids in *W. wallichii*

Table 3. Phenolic acid and flavonoid content in *W. wallichii* by HPLC

Phenolicacids/ flavonoids	Amount (mg/gm dry plant material)	Phenolicacids/ flavonoids	Amount (mg/gm dry plant material)	Phenolicacids/ flavonoids	Amount (mg/gm dry plant material)
Gallic acid	ND	Caffeic acid	ND	Rutin	0.035±0.002
Protocatechuic acid	0.052±0.003	Syringic acid	0.088±0.009	Ellagic acid	ND
Gentisic acid	ND	p-Coumaric acid	0.043±0.002	Myricetin	ND
p-Hydroxy benzoic acid		Ferulic acid	ND	Quercetin	0.024±0.001
Catechin	2.52±0.08	Sinapic acid	ND	Naringenin	ND
Chlorogenic acid	0.0.005±0.0001	Salicylic acid	ND	Apigenin	ND
Vanillic acid	ND	Naringin	ND	Kaempferol	0.06±0.001

Each value in the table was obtained by calculating the average of three experiments and data are presented as Mean ± SEM

2.3.2.3 Biosynthesis of gold nanoparticles using the methanol extract of *W. wallichii*

The leaf extract of *W. Wallichii* is a rich source of different types of plant secondary metabolites in methanol such as phenolic acids (5050±1.14 mg GAE/100g dry material), flavanoids (454.34±0.51 mg/100g dry extract), flavonols (373.21±0.57 mg/100g) etc. HPLC analysis of the leaf extract carried out in our laboratory also supported the presence most of the compounds. The leaf extract of the plant, rich in polyphenolic compounds, can be utilized for the synthesis of AuNPs from HAuCl₄.

2.3.2.4 Synthesis of WW-AuNPs and study of its Surface Plasmon Resonance spectroscopy

The antioxidants including polyphenols are well known for their use in the facile synthesis of metal nanoparticles under very mild condition. As the leaf extract of *W. wallichii* was rich in easily oxidisable plant secondary metabolites including polyphenols, the methanol extract was utilized for the green synthesis of AuNPs at room temperature. To test this, the methanol extract of the plant, contained in vials was treated with HAuCl_4 solution (Fig.2). The appearance of violet to pinkish red coloration after 10 minutes indicating the formation of WW-AuNPs. The intensities of the colours increased on standing the solutions at room temperature for several hours and then remained constant and the WW-AuNPs once formed were stable for several months at room temperature.

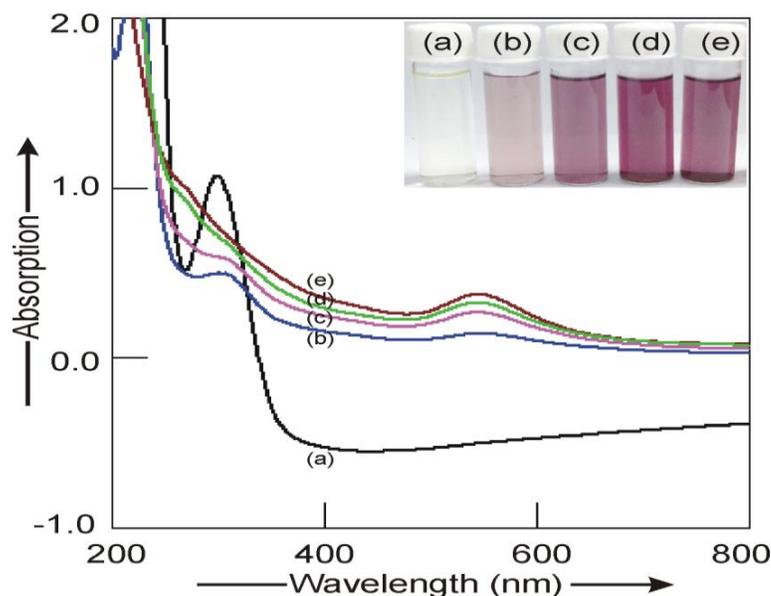


Fig. 2. UV-visible spectra of (a) HAuCl_4 (0.67 mM), (b-e) AuNPs at 100, 200, 300, and 400 mgL^{-1} concentrations of leaf extract respectively. Inset: Photograph of the vials containing (a) HAuCl_4 (0.67 mM) solution, (b-e) colloidal AuNPs at 100, 200, 300 and 400 mgL^{-1} of leaf extract respectively (after 24 h of mixing)

The HAuCl_4 showed a strong peak at 243 nm and a shoulder peak at 298 nm. This was due to the charge transfer interactions between the metal and the chloro ligands (Fig.2a). The intensities of these two peaks decreased with increasing concentration of the leaf extract of *W. wallichii* and new peaks appeared around 530 nm. This is due to surface plasmon resonance (SPR) of the AuNPs, a phenomenon arising due to collective oscillation of the conduction band electrons interacting with the electromagnetic component of the visible light. With increasing the concentration of the leaf extract, a blue shift of the SPR band was observed due to the formation of smaller sized AuNPs. The shoulder peaks observed in the 270-275 nm regions of AuNPs colloids were due to the formation of quinone moiety formed by the oxidation of the phenolic compounds.

2.3.2.5 Mechanism of the formation of Stabilized AuNPs

The leaf extract of *W. wallichii* is a rich source of different types of phytochemicals including polyphenols, flavanoids, flavonols, etc. The *O*-dihydroxy compounds present in the leaf extract can form a five member chelate ring with the Au(III) ions. Au(III) ions having a very high reduction potential can be reduced to Au(0) with concomitant oxidation of the polyphenols to corresponding quinones. The freshly generated Au(0) atoms in the reaction mixture can collide with each other forming AuNPs which are stabilized by the concomitantly formed quinones, polyphenols and other coordinating phytochemicals. The steric bulk of the backbone of the benzoquinones derivative and other phytochemicals wrapping around the nanoparticles provide robustness against further aggregation of the stabilized AuNPs (Fig. 3).

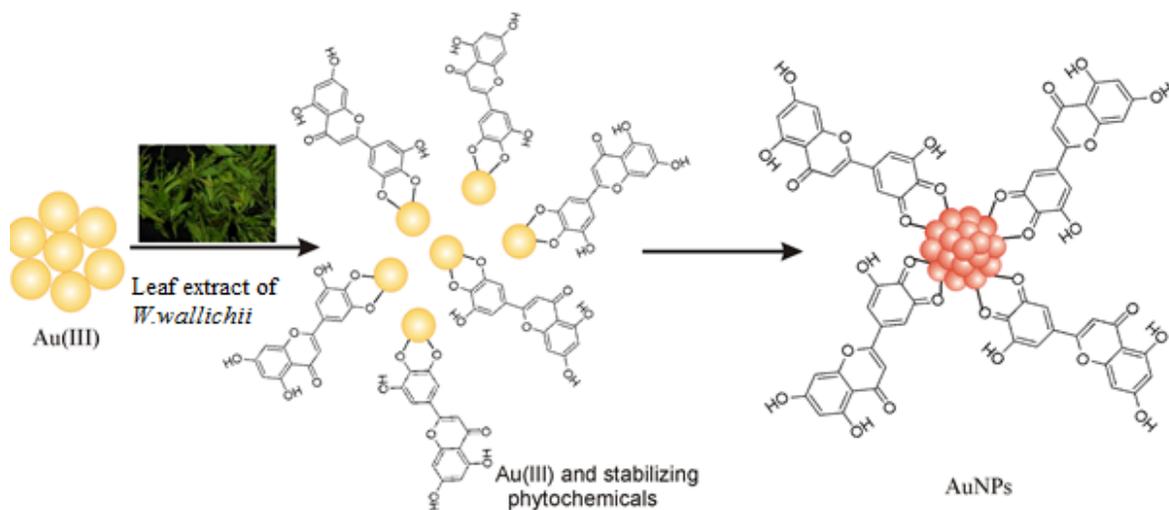


Fig. 3. Mechanism of the formation and stabilization of AuNPs by the phytochemicals present in the leaf extract of *W. wallichii*

2.3.2.6 HRTEM, SAED, EDX and XRD studies

High resolution transmission electron microscopy (HRTEM) was carried out to study the size distribution, shape and morphology of the AuNPs formed at particular concentration of the leaf extract of *W. wallichii*. AuNPs of spherical, triangular, tetragonal, pentagonal and hexagonal shapes were observed. The average size of the AuNPs formed at 400 mgL⁻¹ concentration of the leaf extract was 10-15 nm (Fig. 4a-d). The polyphenolic compounds, quinone and other chelating phytochemicals present in the leaf extract could effectively stabilize the smaller sized AuNPs. The phytochemicals present in the leaf extract could effectively stabilize the smaller sized AuNPs. The formation of the WW-AuNPs was also confirmed from SAED and EDX analyses which showed the presence of Au along with C from the stabilizing organic ligands (Fig. 4 e,f).

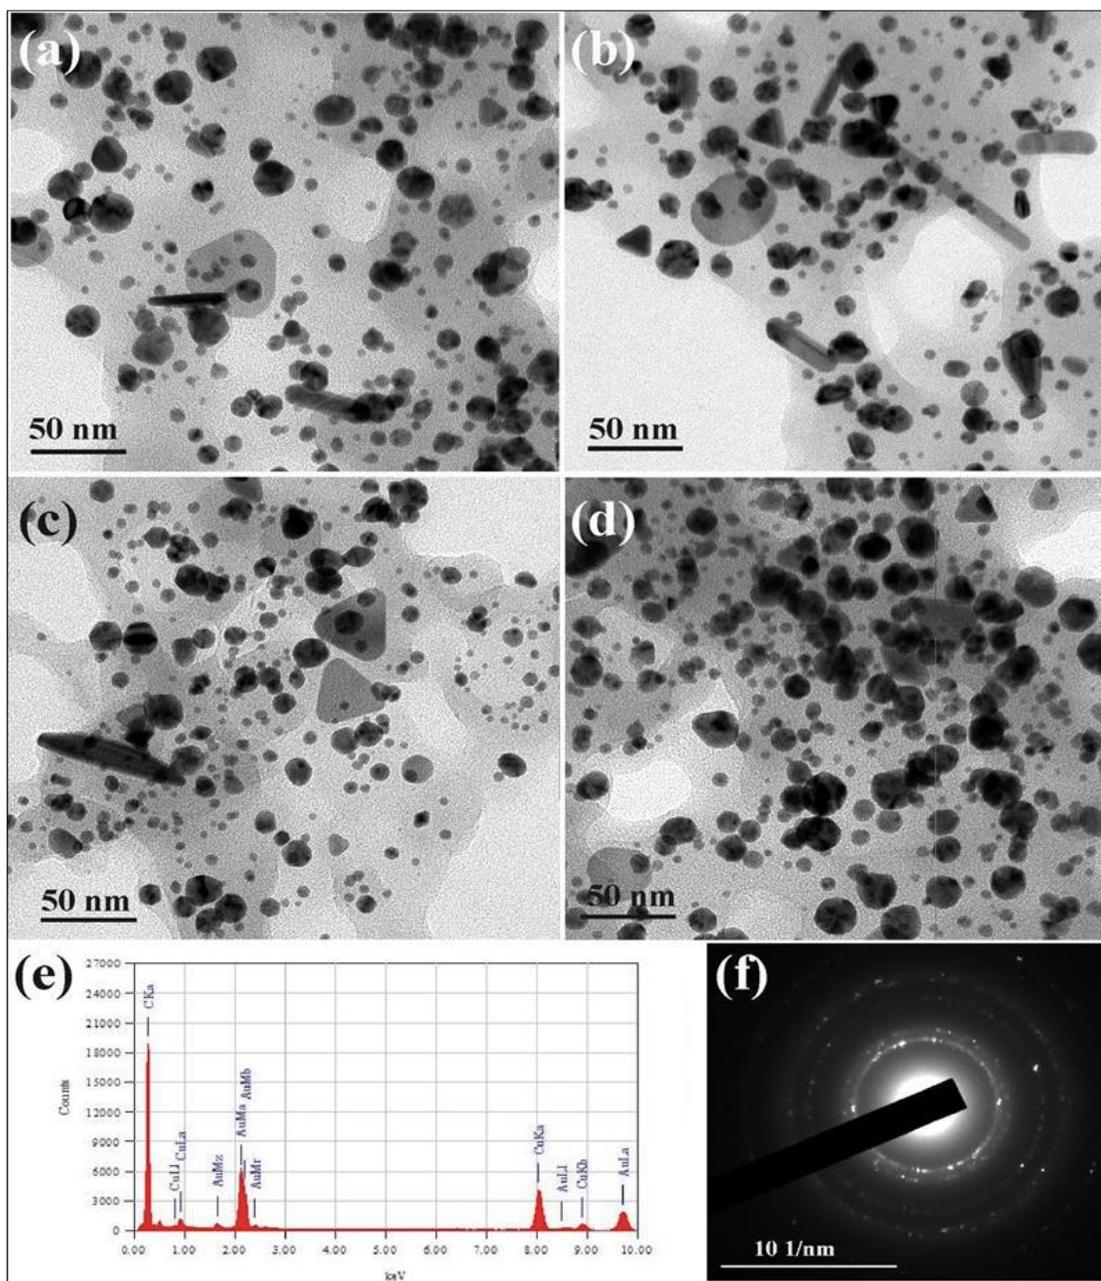


Fig 4: (a-d) TEM Images of AuNPs obtained from the leaf extract of *W. wallichii* at 400 mgL⁻¹, (e) EDX (f) SEAD of stable gold nanoparticles obtained from the leaf extract *W. wallichii* at 400 mgL⁻¹.

High resolution transmission electron microscopy (HRTEM) was carried out to study the size distribution, shape and morphology of the AuNPs formed at particular concentration of the leaf extract of *W. wallichii*. AuNPs of spherical, triangular, tetragonal, pentagonal and hexagonal shapes were observed (Fig. 4a,b). The average size of the AuNPs formed at 400 mgL^{-1} concentration of the leaf extract was 4.85 nm (Fig. 4 c). The polyphenolic compounds, quinone and other chelating phytochemicals present in the leaf extract could effectively stabilize the smaller sized AuNPs. The phytochemicals present in the leaf extract could effectively stabilize the smaller sized AuNPs. The formation of the WW-AuNPs was also confirmed from SAED and EDX analysis which showed the presence of Au along with C from the stabilizing organic ligands (Fig. 4 d,e).

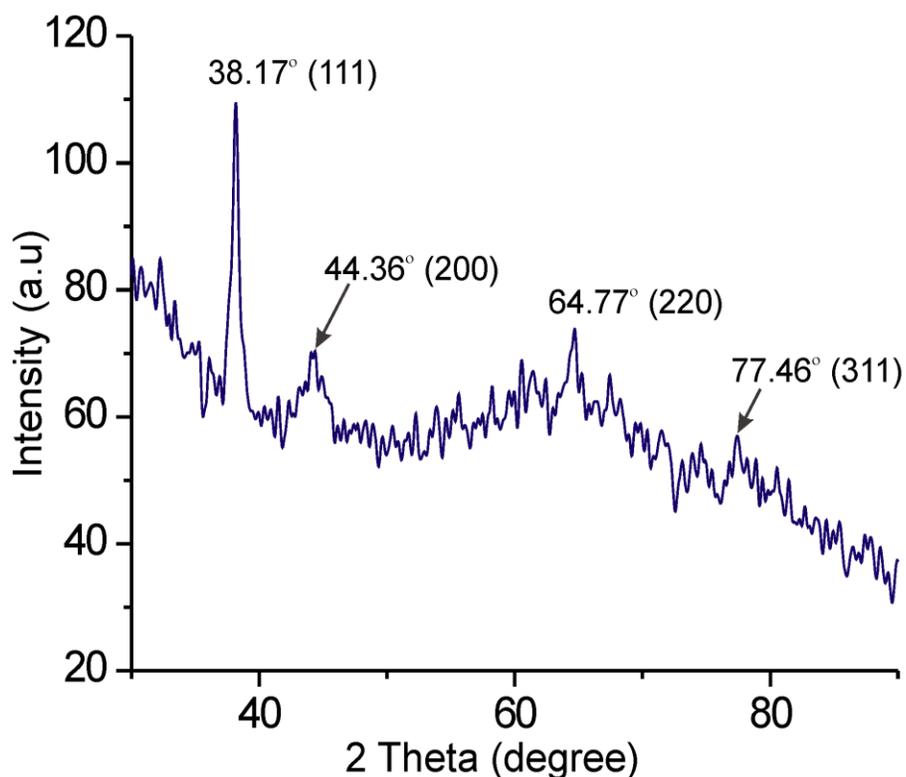


Fig. 5. XRD pattern of stable WW-AuNPs synthesized using the leaf extract of *W. wallichii* (400 mgL^{-1}).

A colloidal WW-AuNPs sample was coated over a glass plate, the volatiles were removed and X-ray diffraction analysis of the dried WW-AuNPs sample was carried out. The reflections of the planes (111), (200), (220) and (311) at $2\theta = 38.17^\circ$, 44.36° , 64.77° and 77.46° respectively (Figure 5) resembled the characteristic reflections of crystalline metallic face centered cubic Au (JCPDS file no. 04-0784). The higher intensity of the 111 plane indicates predominant orientation of this plane compared to the other planes.

2.4. Conclusion

The present investigation showed that this wild edible plant are rich in protein, fat, carbohydrate, fiber and vitamins and could provide essential nutrients required for maintaining normal body function. The nutritional property of this plant was similar to and also sometimes better than the common vegetables. The leaf of the plant was also found to be a significantly useful source of various minerals. The minerals, particularly Na, K, Ca, Fe, Cu, Mg and Zn, were present in appreciable quantities. The antioxidant properties and the presence of various phenolic acids and flavonoids inferred that the leaves of this plant could be used for the nutritional purpose of human being and adequate protection may be obtained against diseases arising from malnutrition. The presence of significant amount of respective bio-active components in this plant under study and variation of quantity determined ensures its usefulness for the synthesis of gold nanoparticles, without requirement of any reducing agent. The high amount of phenolic acids present in *W. wallichii* acted as an electron donor system and ligating agents to form stabilized nanoparticles. Therefore, using this plant extract will be a new and favourable alternative to the current processes to produce metallic nanoparticles in large scale without generating

Chapter 2: Green synthesis of gold nanoparticles using *Wendlandia wallichii*

any toxic by-products. HRTEM studies revealed the mostly spherical shape of the AuNPs of average size of 8 nm. As, *W. wallichii* is non-toxic and edible, *W. wallichii*-conjugated gold nanoparticles synthesized by the green synthetic method utilizing the active ingredients present in the plant extract will be useful for various biomedical as well as nano-scientific applications.

2.5. References:

1. Dahl J.A., Maddux B.L., Hutchison J.E. *Chem. Rev.*: 2007; 107 : 2228-2269.
2. Hutchison J.E. *ACS Nano* : 2008; 2 : 395-402.
3. Sharma V.K., Yngard R.A., Lin Y. *Adv. Colloid Interface Sci.* : 2009; 145 : 83-96.
4. Schmid G., *Clusters and Colloids: From theory to applications*, VCH, Wienheim, 1994.
5. I. Pastoriza-Santos, Liz-Marzan L.M. *Langmuir* : 2002; 18 : 2888-2894.
6. Dong S., Zhou S. *Mater. Sci. Eng. B* : 2007; 140 : 153-159.
7. Jingquan C., Suwei Y., Weiguo Z., Zou Y. *Chem. China* : 2006; 4 : 418-422.
8. Rao Y.N., Banerjee D., Datta A., Das S.K., Guin R., Saha A. *Radiat. Phys. Chem.* : 2010 ; 79 : 1240-1246.
9. Yin B., Ma H., Wang S., Chen S. *J. Phys. Chem. B* : 2003; 107 : 8898-8904.
10. Shankar S.S., Rai A., Ahmad A., Sastry M. *J. Colloid Interface Sci.* : 2004; 275 : 496-502.
11. Tao A., Sinsermsuksaku P., Yang P. *Angew. Chem. Int. Ed.*: 2006; 45 : 4597-4601.
12. Hebeish A.A., El-Rafie M.H., Abdel-Mohdy F.A., Abdel-Halim E.S., Emam H.E. *Carbohydr. Polym.* : 2010; 82 : 933-941.
13. Anastas P.T., Warner J.C. *Green Chemistry: Theory and practice*. Oxford University Press, New York, 1998.
14. Raveendran P., Fu J., Wallen S.L. *J. Am. Chem. Soc.* : 2003; 125 : 13940- 13941.
15. Xie J, Lee S, Chen X. *Adv. Drug Deliv. Rev* : 2010; 62, 1064-1079.
16. Ahmad R, Sardar M. *Biochem. Anal. Biochem* : 2015 ; 2, 1000178.
17. Salata O.V. *J Nanobiotech* : 2014; 2 :32.
18. Rodriguez P, Plana D, Fermin D.J, et al. *Chinese J Catal.* : 2014; 311:182-189.

Chapter 2: Green synthesis of gold nanoparticles using *Wendlandia wallichii*

19. Bar H. et al. *Colloids Surf. A* : 2009 ; 339 : 134-139 .
20. Cruz D. et al. *Colloid Surf. B* : 2010 ; 81 ; 67-73. .
21. Awwad A.M, Salem N.M, Abdeen A.O. *Int J Ind Chem* : 2013; 4: 1-6.
22. Babu P.J., Das R.K., Kumar A, et al. *Int J Green Nanotech* : 2011; 3: 13-21.
23. Seal Tapan, Pillai Basundhara, Chaudhuri Kausik. *Journal of Food and Nutrition Research* : 2017; 5(1) : 1-5.
24. Hedge J.E, Hofreiter B.T. In: *Carbohydrate Chemistry*, 17(Eds. Whistler R.L. and Be Miller, J.N.), Academic Press, New York, 1962.
25. Guil-Guerrero J.L, Gimenez-Gimenez A, Rodriguez-Garcia I, Torija-Isasa M.E. *J Sci Food Agric* : 1998 ;76 : 628-632.
26. Indrayan A.K, Sharma S, Durgapal D, Kumar N, Kumar M. *Current Science* : 2005; 89 ; 1252-1255.
27. Seal Tapan, Chaudhuri Kausik, *International Journal of Pharmaceutical Sciences and Research* : 2015 ; 6(12) : 5134-5140.
28. Seal Tapan, Chaudhuri Kausik, Pillai Basundhara, *Journal of Pharmacognosy and Phytochemistry* : 2017; 6(6): 1837-1847.
29. ICH-Q2A, *Text on Validation of Analytical Procedures*, March 1995.
30. ICH-Q2B, *Validation of Analytical Procedures: Methodology*, November 1996.
31. Hasan Sk. N., Paul K., Dey A., Manna S., Roy S., Bag B.G., Mondal S. *Int. J. Res. Chem. Environ* : 2017 ; 7(2) : 1-8.
32. Satter M.M.A, Khan M.M.R.L, Jabin S.A, Abedin N, Islam M.F, Shaha B. *Asian Pacific Journal of Tropical Biomedicine* : 2016 ; 6 : 125-131.
33. Sundriyal M, Sundriyal R.C. *Economic Botany* : 2004; 58 : 286-299.

Chapter 2: Green synthesis of gold nanoparticles using *Wendlandia wallichii*

34. Koca I, Hasbay I, Bostanci S, Yilmaz V.A, Koca A.F. Pak J Nutr : 2015; 14 : 188-94.
35. Saupi N, Zakaria M. H, Bujang, J. S. Journal of Applied Science : 2009; 9 : 2969-2974
36. Ihedioha J. N, Okoye C.O.B. American Journal of Plant Nutrition and Fertilization Technology : 2011; 1 : 55-63.
37. Saikia P, Deka D.C. Journal of Chemical and Pharmaceutical Research: 2013; 5: 117-12.
38. Florence O.J, Adeolu A. A, Anthony J. A. Rec Nat Prod.: 2011; 5: 29-42.
39. Pourmorad F, Hosseinimehr S. J, Shahabimajd N. Afr J Biotechnol.: 2006; 5: 1142-45.
40. Ramadoss Karthikeyan ,SI.,Devadasu, Chapala, Srinivasa Babu Puttagunta. International Journal of Analytical Chemistry : 2015; 2015: 1-7.
41. Viviane Marques, Adriana Farah. Food Chemistry : 2009 ; 113(4), 1370-76.
42. Seal T, Pillai B, Chaudhuri K. Journal of Chemical, Biological and Physical Sciences : 2016; 6(4): 1108-1121.
43. Sepulveda L, Ascacio A, Rodríguez-Herrera A.R, Aguilera-Carbo A, Aguilar Cristóbal, N. African Journal of Biotechnology : 2011; 10 : 4518-4523.
44. Wach A, Pyrzyńska K and Biesaga M. Food Chemistry: 2007; 100: 699–704.